



Nonlinear Conductivity Theory Research of Composite Materials

Peng HU ^{a*}

^a *School of Materials Science and Engineering, North China University of Water Resources and Electric Power, Zhengzhou, 450045, China.*

Author's contribution

The sole author designed, analyzed, interpreted and prepared the manuscript.

Article Information

Open Peer Review History:

This journal follows the Advanced Open Peer Review policy. Identity of the Reviewers, Editor(s) and additional Reviewers, peer review comments, different versions of the manuscript, comments of the editors, etc are available here: <https://www.sdiarticle5.com/review-history/127176>

Received: 08/09/2024

Accepted: 14/11/2024

Published: 19/11/2024

Minireview Article

ABSTRACT

Composite materials with nonlinear conductivity characteristics are widely used to solve the problem of electric field concentration in the insulation of cable accessories. In this paper, the conductive mechanism and influencing factors of related inorganic conductive particles and polymer matrix are systematically summarized, especially the key problems in the study of nonlinear conductivity of composite materials are put forward. Several mechanisms and applicable conditions in various conduction theories are analyzed, and the effects of filler type, content and temperature on the conductivity of composites are illustrated with examples. Then, the research progress of nonlinear conductivity theory of composite materials is reviewed, and the co-blending of single filler with multi-dimension filler and its application in nonlinear conductive materials are introduced. The purpose of this paper is to give researchers a full understanding of the current research status of nonlinear conductivity. We believe that this work is of great significance for the study of nonlinear conductivity.

*Corresponding author: Email: 1539684540@qq.com;

Keywords: Polymer materials; nonlinear conductivity; conductive mechanism; homogenizing electric field; inorganic filler.

1. INTRODUCTION

High-voltage direct current (HVDC) transmission technology has been widely applied in the field of power transmission due to its advantages of low current loss, large transmission capacity, high operational stability, low environmental impact, and economic efficiency [1]. However, cable accessories, as an indispensable part of power cable systems, often become the most frequent failure points. According to the statistical data on faults in power cable systems, cable accessories account for up to 70% of all faults [2]. This is mainly because in DC systems, the insulating polymer is easily charged and accumulates charges when subjected to external conditions, leading to uneven electric field distribution within the insulation. Under the combined effects of space charge accumulation, local discharge, overheating, and electrode branching, the insulating performance of the polymer gradually deteriorates, ultimately leading to irreversible breakdown [3-4].

In order to deal with this problem, as early as the 1960s, some scholars proposed the use of materials with certain conductance characteristics to optimize electric field distribution. However, the problem of concentration of electric field intensity in cable attachment media has not been studied in depth [5]. Subsequently, through the unremitting exploration of scholars at home and abroad, it is found that the use of nonlinear conductivity composite materials can maintain good insulation properties under normal working conditions. When the accumulation of space charge causes the internal field strength to reach a specific threshold, these materials can accelerate the release of space charge through the transient high conductivity mechanism, thus ensuring that the electric field strength inside the cable attachment medium is always maintained within a relatively safe range [6-9].

In this paper, the conductive mechanism and influencing factors of inorganic conductive particles and polymer matrix are summarized, and the research progress of nonlinear conductive materials is reviewed in order to provide a new reference scheme for HVDC transmission.

2. CONDUCTION MECHANISM OF NONLINEAR CONDUCTIVE COMPOSITES

At present, regarding the electrical conduction mechanism of electric field-controlled composite materials, the generally accepted theories include percolation theory, effective medium theory, quantum tunneling effect theory, field emission theory, etc. [10] These theories explain the electrical conduction mechanism of composite materials under different conditions from different perspectives.

2.1 Percolation Theory

In 1957, J. M. Hamersley proposed the percolation theory for the first time in the study of liquid flow phenomena in disordered porous media. Later, it was found that percolation is also common in polymer composites, and conductive composites can be prepared by adding a certain amount of conductive particles to the insulating polymer matrix, which is precisely because there is a "percolation phenomenon" between the concentration of conductive particles in the polymer matrix and the conductivity of the composite material, that is, with the increase of the concentration of filler in the composite material, The conductivity of the composite material is not proportional to the increase, but when the concentration of the filler particles inside the composite material increases to a threshold, the conductivity will increase abruptly, and the change range is very obvious. After this threshold, the conductivity of the composite slowly increases as the packing concentration continues to increase [11-13]. Specifically described as: when the concentration of the conductive filler is low, the average distance between the filler inside the polymer matrix is large, at this time, the conductivity of the composite material is mainly considered to be the conductivity of the polymer matrix. When the concentration of conductive fillers in the polymer continues to increase, the average distance between the fillers inside the polymer will gradually decrease, until the concentration of the filler exceeds a certain critical value, a conductive network can be formed between the filled particles, thus making the conductivity of the composite material suddenly increase, this phenomenon is called percolation phenomenon. The critical value is called the percolation

threshold [14-15]. Percolation theory is a macroscopic explanation of the conductivity phenomenon of composite materials, which does not involve the essence, but can be widely used because it is easy to understand.

2.2 Effective Medium Theory

The effective medium theory can not only be used to study and explain the influence of the relationship between matrix and filler on the conductivity of composite materials, but also to explain the influence of the basic microscopic morphology and distribution of filler on the overall conductivity, and is also helpful in predicting the conductivity of some composite materials [16]. Effective medium theory can be divided into two parts: classical effective medium theory and universal equation theory of effective medium. Among them, the classical effective theory can be understood as the average theory in essence, ignoring the small-range effect around the seepage threshold, so it is not easy to hold within the overall doping amount range, which is divided into two theories of homogenization and non-homogenization, respectively proposed by Bruggeman and Maxwell-Garnett [17-18]. In order to make up for the shortcomings of the effective medium theory, McLachlan proposed the universal equation of effective medium [19]. However, since the premise of this theory is to require the doping to be 100% full of the entire polymer, the practical application of this theory is greatly limited [20].

2.3 Quantum Tunneling Theory

The theory was first introduced in 1963, and is a universal tunnel conduction equation derived by Simmons based on quantum theory. It can be described as follows: under different applied voltages, the insulation between electrodes will have a potential barrier that changes in size and width, and this microscopic difference will lead to a change in the current density of the composite material on the macro level. In view of other studies and theoretical analysis, the theory explains the conductive mechanism of composite materials as follows: when the spacing of conductive fillers in the composite materials is very small, electrons will transition between them to form a conductive network, so that the composite materials conduct electricity. However, when there are fewer fillers, the spacing between fillers is too large to form current conduction, and the tunneling current of the composite material will decrease

exponentially, that is, the tunneling phenomenon only occurs between conductive fillers very close to each other [21-23].

2.4 Field Electron Emission Theory

This theory is similar to the quantum tunneling effect theory, which both believe that the tunneling effect is the main behavior of the composite material's electricity conduction, but the field electron emission theory has a different explanation for the cause of electron tunneling. According to Beek's research, the tunneling effect should be a special case of field emission inside conductive particles. When the distance between conductive particles is less than 10 nm, the field intensity between the particles will be very large, and the conductive particles will interact with each other and transfer charges, resulting in the generation of current [24-27].

To sum up, both quantum tunneling theory and field electron emission theory believe that the conductivity of composite materials is related to the size of the applied field strength. In addition, other theories believe that the conductivity of composite materials is related to the concentration of fillers and other factors. In most cases, the conductive mechanism of polymer composites may be a combination of multiple theories, so it is relatively complex.

3. FACTORS AFFECTING NONLINEAR CONDUCTIVITY CHARACTERISTICS

In practical applications, the selection of polymer matrix is generally fixed, so the type, content and temperature of filler are the key factors affecting the nonlinear conductivity of composite materials.

3.1 Influence of Filler Type and Content

The conductivity characteristics of different fillers are different. Take the most common modified fillers as an example, ZnO is an anisotropic ceramic material, and its nonlinear conductivity characteristics are due to the typical disordered grain boundary structure inside. The nonlinear conductivity characteristics of SiC are derived from the particle surface oxidation, field emission and local heating theories, etc. Both of these fillers can effectively improve the nonlinear coefficient of composite materials [28]. However, carbon allotrope has a high conductivity, which can significantly improve the conductivity of composite materials when used as modified fillers, but the improvement of nonlinear coefficient is very limited, and the high content of

fill will lead to the loss of nonlinear conductivity of composite materials [29]. Therefore, it can be concluded that the size, shape and grain boundary of the same kind of filler will also affect the nonlinear conductivity characteristics of the composite material, and we can improve the performance of the nonlinear conductivity composite material by adjusting the above parameters.

3.2 Influence of Temperature

The insulating materials in HVDC cables are mostly polymer insulating materials, which have low heat conduction. The conductivity of insulating materials is greatly affected by temperature. When there is a temperature gradient in DC equipment, the conductivity of insulating materials will change significantly, resulting in local charge accumulation and changes in electric field distribution, which will adversely affect the service life of insulating materials. Therefore, it is necessary to study thermal insulation materials.

Huang et al. concluded by finite element simulation that the temperature gradient would cause the accumulation of heteropolar charge on the low temperature side of the anode of XLPE, resulting in the distortion of the electric field, and with the increase of the temperature gradient, the distortion rate of the electric field would also increase [30].

Teng et al. doped PDA-coated (BT60) particles into epoxy resin matrix to prepare composite materials. It is found that this method can significantly optimize the resistivity and temperature characteristics, thus optimizing the distribution of the DC electric field and maintaining the DC breakdown strength. The DC breakdown strength of the epoxy composite containing 20 wt% BT60-PDA is 99.5% of that of pure epoxy at 90 °C, while the simulated maximum electric field is 49% lower compared to the latter [31].

Zhang et al. uniformly dispersed boron nitride nanosheets (BNNs) in the SEBS phase to construct a thermal conductivity network structure based on the dual seepage process. The results show that the introduction of BNNs significantly improves the direct current (DC) breakdown strength and space charge suppression. In addition, the thermal conductivity of the composite has increased threefold [32].

The conductivity characteristics of nonlinear conductivity composites are determined by the

properties of the material and the external environment, so the influence of temperature on the nonlinear threshold field strength and nonlinear coefficient should be fully considered when designing the nonlinear conductivity modification scheme.


4. MEASURES TO IMPROVE THE PROPERTIES OF NONLINEAR CONDUCTIVE COMPOSITES

The addition of modified fillers is essentially to introduce impurities into the polymer matrix, and the content of the filler is too low to ensure the stability of the nonlinear conductivity of the composite. If the content is too high, the interface gap of the composite dielectric will lead to accelerated aging and deterioration, and the breakdown strength will be greatly reduced. In addition, due to the involvement of high-voltage insulation equipment, electronics industry, and spacecraft components and other application fields, the nonlinear threshold field strength and non-linear coefficient need to adapt to different application scenarios, and the thermal conductivity and mechanical strength of the composite material after the introduction of the filler can be adapted to the working environment for a long time should also be taken into account.


In recent years, scholars at home and abroad have devoted themselves to the study of improving the comprehensive properties of nonlinear conductive materials and the control of non-linear parameters. He et al. summarized the methods to improve the properties of nonlinear conductance composites and regulate the parameters of nonlinear conductance composites, which mainly include: artificial control of filler distribution, the use of nano-filler with high aspect ratio, the influence of polymer matrix, the influence of internal grain boundaries of the filler and the shape of the filler on the nonlinear parameters, and the addition of a second filler [33]. It is more feasible to control the parameters of the filler itself and introduce a second filler, which is mainly used to improve the performance of nonlinear conductive materials.

4.1 Parameter Control of a Single Filler


The dimension, size, shape and grain boundary of the filler are the key factors that affect the nonlinear conductivity of the composite. By adjusting the parameters of the filler itself, the seepage threshold of the filler can be effectively reduced and the nonlinear conductivity of the composite can be adjusted.

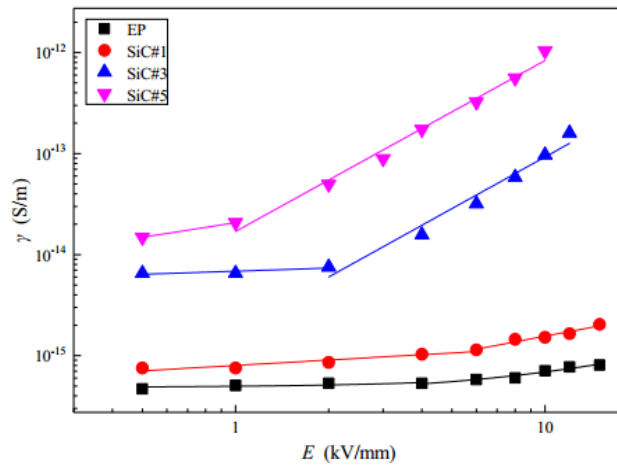

(a) nano-SiC/EP composites

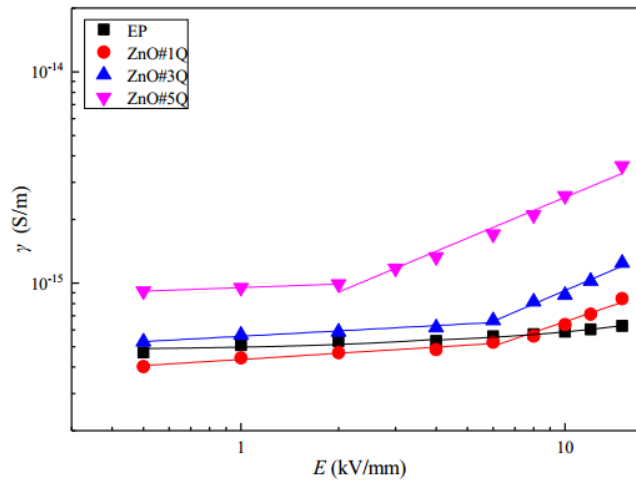

(b) nano-ZnO/EP composites

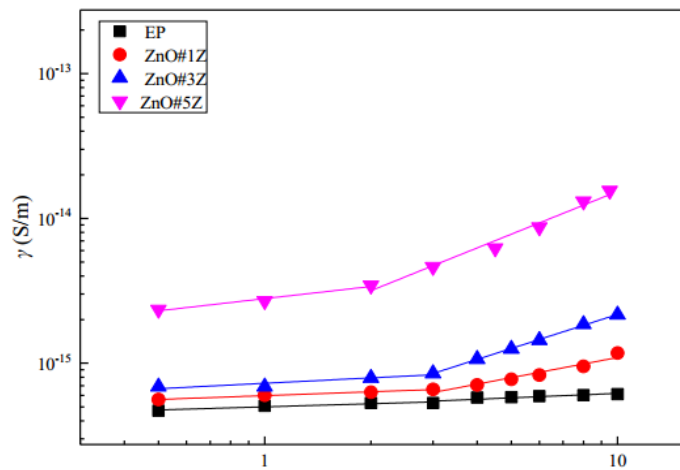

(c) micro-ZnO/EP composites

Fig. 1. γ -E characteristic curves of composites for different filler concentrations (with respect to EP) [33]



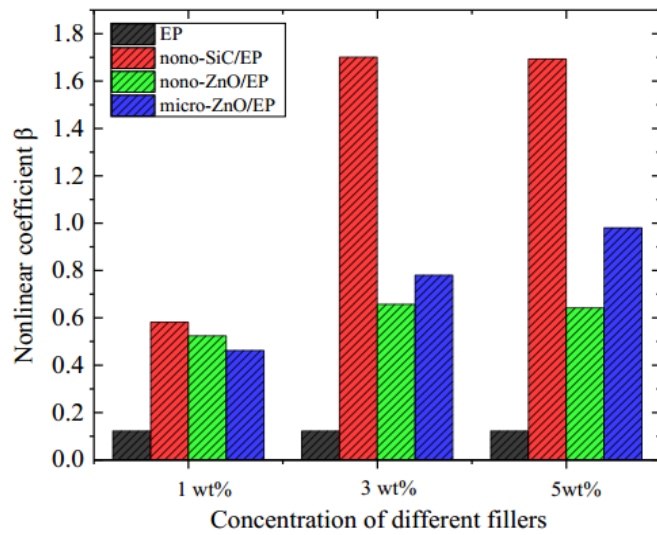


Fig. 2. Nonlinear coefficients of three composite materials at different mass fractions [33]

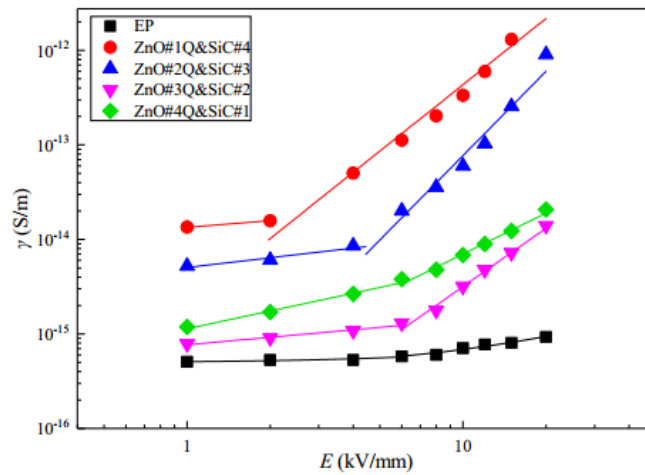


(a) nano-ZnO/SiC/EP nanocomposites

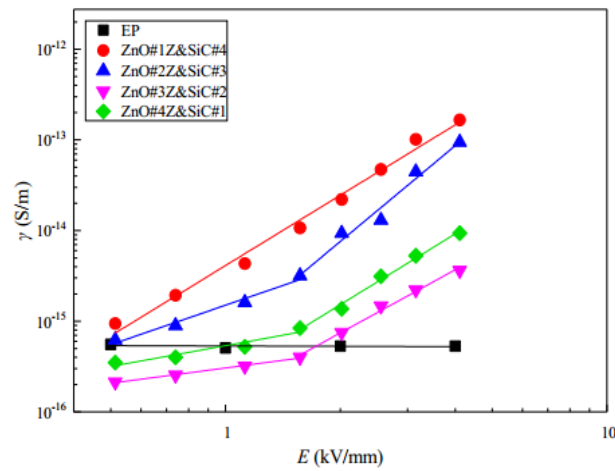


(b) micro-ZnO/SiC/EP micro/nanocomposites


Fig. 3. γ -E characteristic curves of composite materials with different proportions [33]

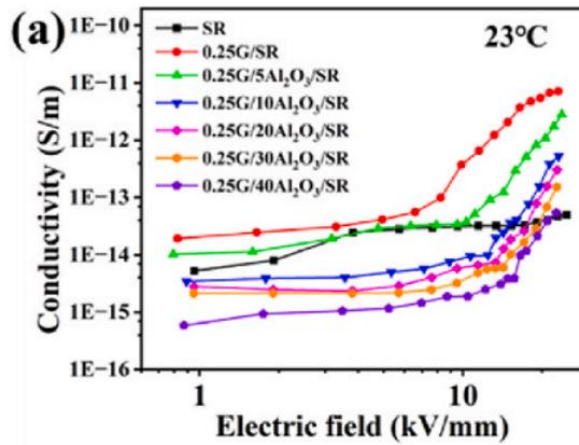

(a) 23 °C

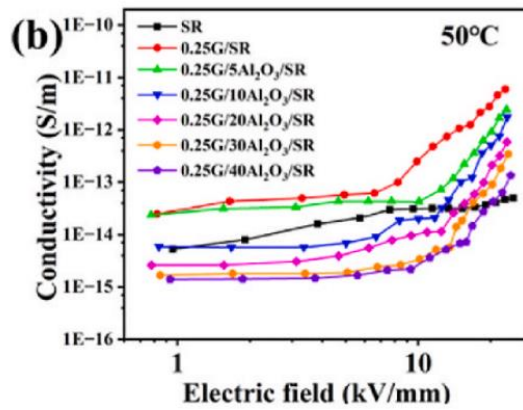

(b) 50 °C

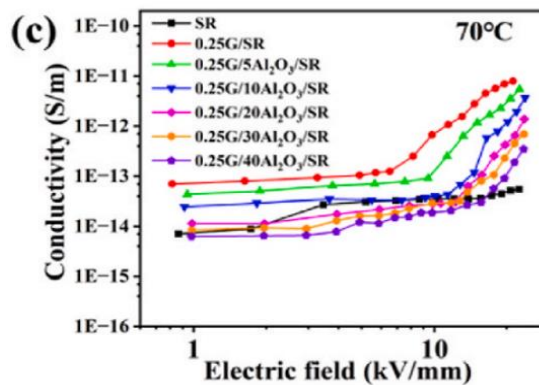

(c) 70 °C

Fig. 4. DC conductivity at different temperatures of the G/Al₂O₃/SR composites[39]

In order to study the uneven distribution of electric fields in insulated devices and components, Hu et al. used nano-sic, nano-ZnO and micro-ZnO particles as fillers. Five kinds of nonlinear conductive composites based on epoxy resin (EP) were prepared (nano-SiC/EP, nano-

ZnO/EP, micro-ZnO/EP, nano-SiC/ZnO/EP and nano-micro-SiC/ZnO/EP). The mass fraction of inorganic fillers was 1, 3 and 5 wt%, respectively. The DC voltage characteristic results of the composite are shown in Figs. 1-3. The conductivity and nonlinear coefficient of the

composite increase with the increase of inorganic filler content. Under the same conditions, the conductivity and nonlinearity of SiC/EP are higher than nano-ZnO/EP and micro-ZnO/EP. The addition of zinc oxide and sic at the same time has a significant effect on the nonlinear coefficient of the composite. When the ratio of micro-ZnO to nano-SiC is 2:3, the nonlinear coefficient of the composite reaches a maximum of 3.506, which is significantly higher than that of other samples. Compared with nano-SiC/EP, micro-ZnO/EP and nano-ZnO/EP composites with inorganic filler content of 5 wt%, the nonlinear coefficients of the composites are increased by 0.82, 2.48 and 5.01 times, respectively [34].

In order to solve the problem of mechanical degradation of nonlinear conductivity composite materials with high filling content, Gaska and other scholars prepared graphite nanosheets/low density polyethylene (LDPE) composite materials. When the mass fraction of the filler was only 5%, The composite material has shown obvious nonlinear conductivity characteristics, and its mechanical properties are almost at the same level as before modification [35]. Nie et al. use silver-coated zinc oxide whiskers to modify silicone rubber materials, so that the pressure sensitive field strength of silicone rubber composite materials can be significantly reduced and the nonlinear coefficient can be increased at a lower filler content [36].

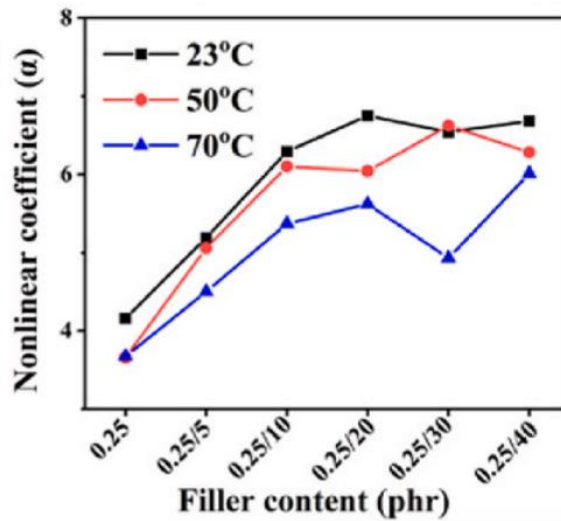


Fig. 5. The nonlinear coefficient α of the G/Al₂O₃/SR composites [39]



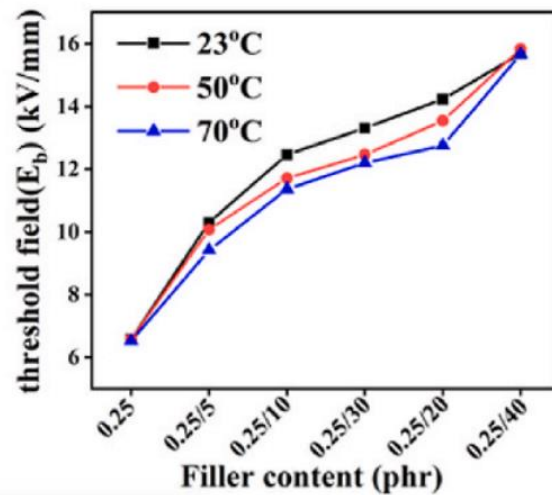



Fig. 6. the threshold field strength E_b of the G/Al₂O₃/SR composites [39]

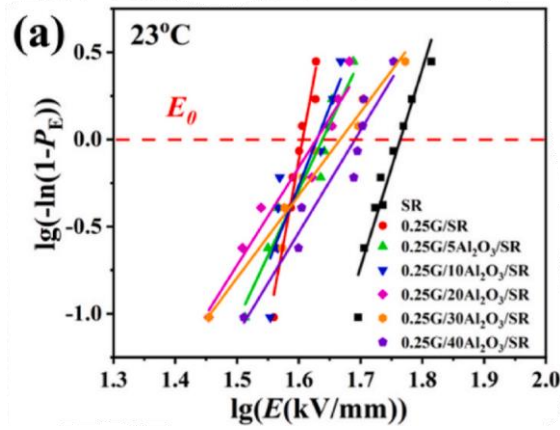

(a) 23 °C

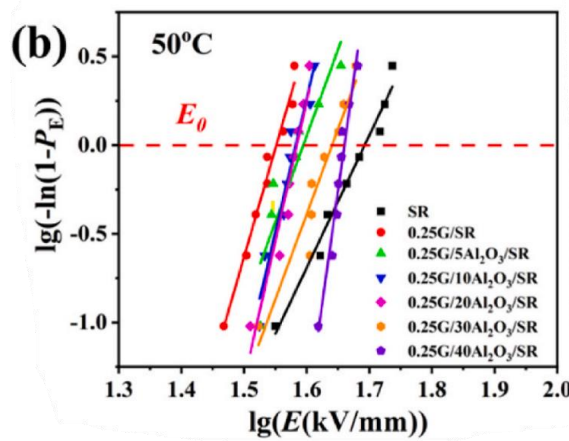

(b) 50 °C

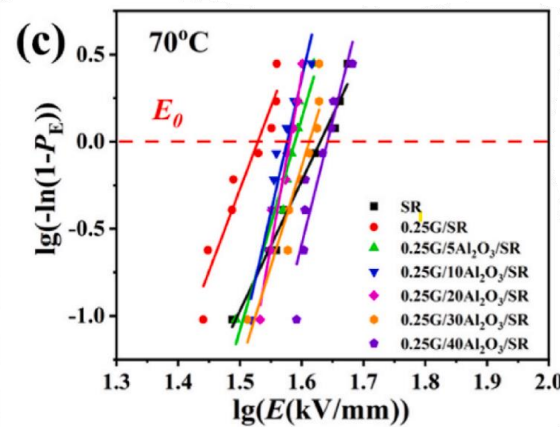

(c) 70 °C

Fig. 7. The Weibull distribution of breakdown strength at different temperatures of the G/Al₂O₃/SR composites [39]

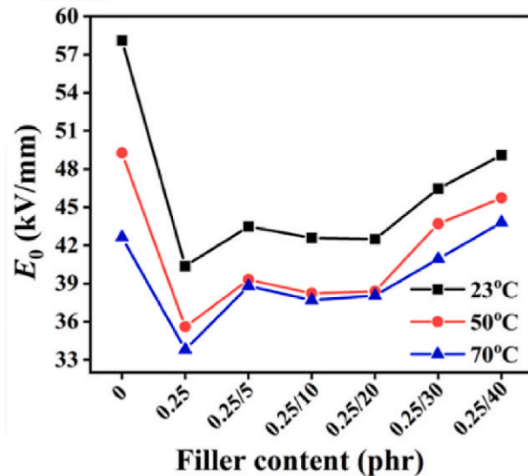


Fig. 8. The characteristic breakdown field E_0 of the G/Al₂O₃/SR composites [39]

4.2 Adopting Ternary Compound System

Although the properties of the composites can be significantly improved by adjusting the parameters of the filler itself, the modification effect of a single filler on the polymer matrix is limited. In order to further improve the comprehensive energy of the composite material, a second filler is needed [37]. The scheme of using ternary composite system to improve the nonlinear conductivity of composite materials was proposed by Hidehito Matsuzaki and other scholars from Toshiba Corporation of Japan. By adding small diameter conductive or semi-conductive particles into ZnO/polymer system, more conductive channels can be formed under the condition of lower filler content. A nonlinear conductivity composite with excellent properties was obtained [38-39]. With the development of the material field, there are more options for second fillers.

Yang et al. used silicone rubber-based materials with nonlinear conductivity to improve the field distortion and charge accumulation problems in cable accessories by adding graphene (G; 0.25 phr) and alumina particles (Al₂O₃; 5-40 phr) to SR to obtain good nonlinear electrical conductivity and relatively high breakdown strength, as well as thermal conductivity. The results are shown in Figs. 4-8. At 23 °C, the nonlinear conductivity α of 0.25G/40Al₂O₃/SR composite reaches 6.68, and the breakdown field strength E_0 is 49.1kV/mm, which is comparable to that of pure SR. In addition, at 23 °C, the thermal conductivity of 0.25G/30Al₂O₃/SR is 0.28Wm⁻¹ K⁻¹, which is 114.98% higher than that

of pure SR, indicating the application prospect of G/Al₂O₃/SR composites as cable components [40].

Iranian scholars Mashkouri et al used two-dimensional laminated exfoliated graphite (EG) to make the original ZnO/ high density polyethylene (HDPE). The pressure sensitive field strength of the HDPE composite system can be adjusted in the range of 40~400 kV/m, so as to meet different application requirements. With the increase of EG filler content, the nonlinear threshold field strength of the composite decreases from 400 kV/m to 40 kV/m [41].

5. CONCLUSION

Based on this review it can be concluded as follows

- 1) The nonlinear conductivity of polymer materials is affected by a variety of charge transport mechanisms, but there is no unified theory to explain the nonlinear conductivity mechanism of different composite systems under different external environments.
- 2) The content of the filler in the composite has a certain influence on the formation of the nonlinear conductive seepage path, the injection of charge carriers and the interface effect between the filler and the matrix, thus affecting the difficulty of the formation of the nonlinear conductivity characteristics of the composite.
- 3) The preparation of nonlinear conductive polymer materials shows the trend of filler

development from binary composite to ternary composite, and the new nonlinear conductive composite materials provide more reference schemes for the material selection of cable accessories.

DISCLAIMER (ARTIFICIAL INTELLIGENCE)

Author(s) hereby declare that NO generative AI technologies such as Large Language Models (ChatGPT, COPILOT, etc) and text-to-image generators have been used during writing or editing of this manuscript.

COMPETING INTERESTS

Author has declared that no competing interests exist.

REFERENCES

1. Liu C, Cheng X, Zheng X. Effect of nonlinear conductivity modification on space charge behavior of modified epoxy with inorganic filler[J]. *IEEE Transactions on Plasma Science*. 2023;51(4):1173-1180.
2. Jie C, Shilin W, Libin H. Analysis of insulation state and physicochemical property of retired high-voltage cable accessories[J]. *Transactions of China Electrotechnical Society*. 2021;36(12):2650-2658.
3. Wu K, Su R, Wang X. Space charge behavior in polymeric materials under temperature gradient[J]. *IEEE Electrical Insulation Magazine*. 2020;36(2):37-49.
4. Tan D. Structured microgrids (S μ Gs) and flexible electronic large power transformers (FeLPTs)[J]. *CES Transactions on Electrical Machines and Systems*. 2020;4(4):255-263.
5. Virsberg L. A new termination for underground distribution[J]. *IEEE Transactions on Power Apparatus and Systems*. 1967;PAS-86(9):1129-1135.
6. LEI Weiqun, WU Jiang, PENG Ping, et al. Conduction mechanism analysis of modified polyimide composite[J]. *Journal of Beijing University of Aeronautics and Astronautics*. 2015; 41(6):1049-1054.
7. Gao MZ, Li ZY, Sun WF. Nonlinear conductivity and space charge characteristics of SiC/silicone rubber nanocomposites[J]. *Polymers*. 2022;14(13):2726.

8. Naebe M, Shirvanimoghaddam K. Functionally graded materials: A review of fabrication and properties[J]. *Applied materials today*, 2016, 5: 223-245.
9. Liu C, Zheng X, Peng P. The nonlinear conductivity experiment and mechanism analysis of modified polyimide (PI) composite materials with inorganic filler[J]. *IEEE Transactions on Plasma Science*. 2015;43(10):3727-3733.
10. Li R, Wang Y, Zhang C, et al. Non-Linear conductivity Epoxy/SiC composites for emerging power module packaging: Fabrication, characterization and application[J]. *Materials*. 2020;13(15): 3278.
11. Vaferi K, Vajdi M, Nekahi S, et al. Thermomechanical simulation of ultrahigh temperature ceramic composites as alternative materials for gas turbine stator blades[J]. *Ceramics International*. 2021;47(1):567-580.
12. Taylor N, Edin H. Stator end-winding currents in frequency-domain dielectric response measurements[J]. *IEEE Transactions on Dielectrics and Electrical Insulation*, 2010, 17(5): 1489-1498.
13. Gartner J, Gockenbach E, Borsi H. Field-grading with semi-conducting materials based on silicon carbide (SiC)[C]//Conference Record of the 1998 IEEE International Symposium on Electrical Insulation, Arlington, VA, USA. 2002:202-205.
14. Guo Lei, Ning Shufan, Yu Kaikun, et al. Study progress of silicon carbide non-linear property[J]. *Insulating Materials*. 2005;38(3):60-64.
15. Han Yongsen, Li Shengtao, Min Daomin. Nonlinear conduction and surface potential decay of epoxy/SiC nanocomposites[J]. *IEEE Transactions on Dielectrics and Electrical Insulation*. 2017;24(5):3154-3164.
16. Li Rui, Wang Yufan, Zhang Cheng, et al. Non-linear conductivity epoxy/SiC composites for emerging power module packaging: Fabrication, characterization and application[J]. *Materials*, 2020;13(15): 3278.
17. Zebouchi N, Li Haoluan, Haddad M A. Development of future compact and eco-friendly HVDC gasinsulated systems: Shape optimization of a DC spacer model and novel materials investigation[J]. *Energies*. 2020;13(12): 3288.

18. Wang J, Wang X, Yao Y, et al. Nonlinear electrical characteristics of core-satellite CaCu₃Ti₄O₁₂@ ZnO doped silicone rubber composites[J]. *Rsc Advances*. 2017;7(50):31654-31662.
19. McLachlan DS, Blaszkiewicz M, Newnham RE. Electrical resistivity of composites[J]. *Journal of the American Ceramic Society*. 1990;73(8):2187-2203.
20. He LX, Tjong SC. Direct current conductivity of carbon nanofiber-based conductive polymer composites: effects of temperature and electric field[J]. *Journal of Nanoscience and Nanotechnology*. 2011; 11(5):3916-3921.
21. Köckritz T, Jansen I, Beyer E. Integration of carbon allotropes into polydimethylsiloxane to control the electrical conductivity for novel fields of application[J]. *International Journal of Adhesion and Adhesives*. 2018;82:240-253.
22. Mitic G, Lefranc G. Localization of electrical insulation and partial-discharge failures of IGBT modules[J]. *IEEE Transactions on Industry Applications*, 2002;38(1):175-180.
23. Christen T, Donzel L, Greuter F. Nonlinear resistive electric field grading part 1: theory and simulation[J]. *IEEE Electrical Insulation Magazine*. 2010;26(6):47-59.
24. Donzel L, Schuderer J. Nonlinear resistive electric field control for power electronic modules[J]. *IEEE Transactions on Dielectrics and Electrical Insulation*. 2012; 19(3):955-959.
25. OuYang B, Liu Z, Wang X, et al. Investigation of electrical properties of ZnO@ Ag/EPDM composites[J]. *AIP Advances*. 2020;10(9).
26. Zhonglei L, Yutong Z, Tao H. Research progress and prospect of semi-conductive shielding composites for high-voltage cables[J]. *Transactions of China Electrotechnical Society*. 2022;37(9):2341-2354.
27. Rokhlenko A, Jensen K L, Lebowitz J L. Space charge effects in field emission: one dimensional theory[J]. *Journal of Applied Physics*, 2010, 107(1): 014904.
28. Liu C, Zheng Y, Zhang B, et al. Review of nonlinear conductivity theory research of modified composite materials[J]. *IEEE Access*. 2019;7:50536-50548.
29. Zhao X, Yang X, Li Q, et al. Synergistic effect of ZnO microspherical varistors and carbon fibers on nonlinear conductivity and mechanical properties of the silicone rubber-based material[J]. *Composites Science and Technology*. 2017;150:187-193.
30. Huang X, Feng F, Wu M, et al. Temperature field and space charge analysis of high-voltage DC extruded insulated offshore and terrestrial composite cable[J]. *Insulating Materials*; 2022.
31. Teng C, Zhou Y, Zhang L, et al. Improved electrical resistivity-temperature characteristics of insulating epoxy composites filled with polydopamine-coated ceramic particles with positive temperature coefficient[J]. *Composites Science and Technology*. 2022;221: 109365.
32. Zhang DL, Zha JW, Li CQ, et al. High thermal conductivity and excellent electrical insulation performance in double-percolated three-phase polymer nanocomposites[J]. *Composites Science and Technology*. 2017;144:36-42.
33. He JL, Yang X, Hu J. Progress of theory and parameter adjustment for nonlinear resistive field grading materials[J]. *Transactions of China Electrotechnical Society*. 2017;32(16): 44-60.
34. Hu H, Zhang X, Zhang D, et al. Study on the nonlinear conductivity of SiC/ZnO/epoxy resin micro-and nanocomposite materials[J]. *Materials*. 2019;12(5):761.
35. Gaska K, Xu X, Gubanski S, et al. Electrical, mechanical, and thermal properties of LDPE graphene nanoplatelets composites produced by means of melt extrusion process[J]. *Polymers*. 2017;9(1):11.
36. Nie J, Hou D, Wang G, et al. Preparation and nonlinear conductivity characteristics of silicone rubber filled with silver-coated tetrapod-shaped ZnO whiskers[J]. *Journal of Electronic Materials*. 2019;48:2517-2522.
37. Yao T, Bian W C, Yang Y. Thermal Conductivity and Insulating Property of Epoxy Composites with Micro-BN and Nano-Al₂O₃[J]. *High Voltage Engineering*. 2021;47(01):251-259.
38. Matsuzaki H, Nakano T, Ando H. Effects of second particles on nonlinear resistance properties of microvaristor-filled composites[C]//2012 Annual Report Conference on Electrical Insulation and

- Dielectric Phenomena. IEEE. 2012:183-186.
39. Martensson E, Nettelbled B, Gafvert U, et al. Electrical properties of field grading materials with silicon carbide and carbon black[C]//ICSD'98. Proceedings of the 1998 IEEE 6th International Conference on Conduction and Breakdown in Solid Dielectrics (Cat. No. 98CH36132). IEEE. 1998: 548-552.
40. Yang W, Xue Y, Zhang L, et al. Enhanced nonlinear conductivity of silicone rubber composites with hybrid graphene and alumina for cable accessory[J]. Polymer Testing, 2023, 124: 108080.
41. Mashkouri S, Ghafouri M, Arsalani N, et al. Mechanochemical green synthesis of exfoliated graphite at room temperature and investigation of its nonlinear properties based zinc oxide composite varistors[J]. Journal of Materials Science: Materials in Electronics. 2017;28:4839-4846.

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of the publisher and/or the editor(s). This publisher and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.

© Copyright (2024): Author(s). The licensee is the journal publisher. This is an Open Access article distributed under the terms of the Creative Commons Attribution License (<http://creativecommons.org/licenses/by/4.0>), which permits unrestricted use, distribution, and reproduction in any medium, provided the original work is properly cited.

Peer-review history:

The peer review history for this paper can be accessed here:

<https://www.sdiarticle5.com/review-history/127176>